

## Biosynthesis of silver nanoparticles from *Teucrioside* and investigation of its antibacterial activity

Özlem KAPLAN<sup>1,\*</sup> , Nazan GÖKŞEN TOSUN<sup>2</sup> 

<sup>1</sup>Istanbul University, Department of Molecular Biology and Genetics, Faculty of Science, Istanbul, TURKEY

<sup>2</sup>Tokat Gaziosmanpaşa University, Graduate School of Natural and Applied Science, Department of Biomaterials and Tissue Engineering, Tokat, TURKEY

### Abstract

*Teucrioside*, 9'-decarboxyrosmarinic acid 4'-O- $\alpha$ -rhamnosyl-(1"→6")-O- $\beta$ -galactosyl-(1"→4")-O $\alpha$ -rhamnoside is a natural phenolic compound. It has been isolated and identified from the genus *Teucrium*. *Teucrium* genus is widely used in traditional medicine for its antioxidant, diuretic, antiulcer, antitumor, anti-inflammatory, antispasmodic and antibacterial properties. Since silver nanoparticles have superior physicochemical properties, they have an important role in biology and medicine. In this study, the biosynthesis of silver nanoparticles was carried out using *Teucrioside* and AgNO<sub>3</sub>. The effect of five independent variables (pH, AgNO<sub>3</sub> concentration, *Teucrioside* volume/total volume, microwave power and time) on nanoparticle formation was evaluated using a central composite design (CCD) based response surface methodology (RSM). Nanoparticle formation was demonstrated by UV-Vis spectroscopy and FTIR analysis. The particle size and zeta potential of silver nanoparticles were determined by dynamic light scattering method (DLS). The results showed that 5 mM AgNO<sub>3</sub>, *Teucrioside* volume/total volume:0.3, 475 watt, 60 sec. and pH:7.5 were optimal reaction parameters. The antibacterial activity of biosynthesized silver nanoparticles was tested against common pathogens such as *Enterococcus faecalis*, *Pseudomonas aeruginosa*, *Staphylococcus aureus*, and *Klebsiella pneumonia*. Obtained results demonstrated that biosynthesized silver nanoparticles from *Teucrioside* have great potential as a new antibacterial agent.

### Article info

History:

Received:12.10.2020

Accepted:27.02.2021

Keywords:

*Teucrioside*,  
silver nanoparticle,  
antibacterial activity.

### 1. Introduction

Silver nanoparticles (AgNPs) are very important metallic nanomaterials used in various applications due to their unique optical, electrical and biological properties [1]. The antimicrobial properties of AgNPs have made them widely used in medicine and agriculture [2, 3]. Because of the superior properties of AgNPs such as high antimicrobial activity even at low concentrations, their use reduces the environmental risk associated with excessive antibiotic or pesticide use [4-8]. Bacterial infection and resistance to antibiotics pose a serious threat to human health [9]. AgNPs exhibit adjustable structural properties and broad antibacterial spectrum advantages against antibiotic resistant bacteria. Thus, AgNPs are considered promising antibacterial agents [10]. Flavonoids, aromatic compounds, sugars, polyphenols found in plant extracts are functional groups involved in the biosynthesis of AgNPs [11, 12].

The *Teucrium* genus belongs to the *Lamiaceae* family and has about 300 species widespread all over the world [13]. Due to its pharmacological effects, various species of this genus are used widely in traditional medicine for their antioxidant, diuretic, antiulcer, antitumor, anti-inflammatory, antispasmodic and antibacterial properties [14]. Therefore, interest in *Teucrium* species has increased in recent years. One of the most studied species in the genus is *Teucrium chamaedrys* (germander). Phytochemical constituents of this species comprise flavonoids, diterpenoids and glycosides [13, 15]. Phenylethanoid glycosides are the main phenolic compounds in *Teucrium* species. Recently reports have shown the wide range of biological and pharmacological properties of these components. *Teucrioside* (9'-decarboxyrosmarinic acid 4'-O- $\alpha$ -rhamnosyl-(1"→6")-O- $\beta$ -galactosyl-(1"→4")-O $\alpha$ -rhamnoside) is L-lyxose containing phenylethanoid glycoside found in *Teucrium* genus [13-16]. In this study, it is aimed to synthesize AgNPs in a fast, simple, environmentally friendly and low cost

\*Corresponding author. e-mail address: ozlem.kaplan@istanbul.edu.tr  
<http://dergipark.gov.tr/csj> ©2021 Faculty of Science, Sivas Cumhuriyet University

using *Teucrioside*. The effects of experimental conditions on the biosynthesis of silver nanoparticles were investigated with response surface methodology, the most widely used statistical technique for process optimization [17, 18]. There are studies in the literature regarding the application of response surface methodology in the biosynthesis of AgNPs [19, 20]. The response surface methodology is a useful method for complete, rapid optimization of conditions and the correct design of the synthesis process. Also, antibacterial activity of the synthesized AgNPs was tested against common pathogens such as *Pseudomonas aeruginosa*, *Klebsiella pneumonia*, *Staphylococcus aureus* and *Enterococcus faecalis*.

## 2. Materials and Methods

### 2.1. Biosynthesis of silver nanoparticles and characterization

**Table 1.** The central composite experimental design for *Teucrioside*&AgNPs synthesis

Run	Factor 1 A:AgNO <sub>3</sub> Conc. (mM)	Factor 2 B:Extract Vol./Total Vol.	Factor 3 C:Time(sec)	Factor 4 D:Power (Watt)	Factor 5 E:pH	Response % Yield
1	3	0.1	35	475	3	0
2	5	0.3	60	475	7.5	49.99
3	3	0.1	60	475	7.5	59.58
4	3	0.3	35	150	12	55.12
5	5	0.3	35	475	12	72.33
6	3	0.5	60	475	7.5	37.02
7	3	0.1	35	800	7.5	75.11
8	3	0.5	35	475	3	0
9	1	0.3	60	475	7.5	42.35
10	3	0.3	35	800	3	0
11	3	0.3	10	475	12	65.99
12	3	0.3	10	150	7.5	37.45
13	3	0.3	60	475	12	70.03
14	3	0.3	35	475	7.5	46.52
15	3	0.5	10	475	7.5	43.27
16	3	0.1	10	475	7.5	55.21
17	3	0.3	35	150	3	0
18	1	0.3	10	475	7.5	45.24
19	5	0.3	10	475	7.5	43.88
20	3	0.3	35	475	7.5	46.54
21	1	0.3	35	475	12	59.29
22	5	0.3	35	475	3	0
23	3	0.3	35	475	7.5	46.58
24	3	0.3	35	800	12	100
25	3	0.5	35	150	7.5	33.37
26	3	0.3	60	150	7.5	60.18
27	1	0.5	35	475	7.5	45.12
28	5	0.3	35	800	7.5	75.12
29	1	0.3	35	800	7.5	60.11
30	3	0.3	35	475	7.5	46.49
31	1	0.3	35	150	7.5	46.55
32	5	0.1	35	475	7.5	65.12
33	5	0.5	35	475	7.5	40.49
34	1	0.1	35	475	7.5	50.05
35	3	0.1	35	150	7.5	45.13
36	3	0.3	10	800	7.5	80.15
37	3	0.3	35	475	7.5	46.38
38	3	0.3	10	475	3	0
39	5	0.3	35	150	7.5	35.62
40	3	0.5	35	475	12	50.12
41	3	0.3	60	800	7.5	50.23
42	3	0.1	35	475	12	85.23
43	3	0.3	60	475	3	0
44	1	0.3	35	475	3	0
45	3	0.3	35	475	7.5	46.50
46	3	0.5	35	800	7.5	61.06

### 2.1.3. Synthesis and characterization of *Teucrioside*&AgNPs

*Teucrioside* aqueous solution (5% w/v) was prepared. The biosynthesis of AgNPs was carried out using different pH,  $\text{AgNO}_3$  concentration, *Teucrioside*/ $\text{AgNO}_3$  ratio, microwave power and time. The mixture was centrifuged at 20.000 g for 10 minutes and AgNPs were precipitated. The AgNPs were washed with distilled water and they were dried overnight at 37°C. Biosynthesis of AgNPs were confirmed by UV-Vis spectroscopy and FTIR analysis. The particle size and zeta potential analysis of synthesized AgNPs were determined by dynamic light scattering method using HORIBA SZ-100 Nanoparticle Analyzer.

### 2.2. Antibacterial activity of *Teucrioside*&AgNPs

Antibacterial activity was studied with two gram negatives bacterium (*Pseudomonas aeruginosa* (ATCC 27853) and *Klebsiella pneumonia* (ATCC 15380)) and two gram positive bacterium (*Enterococcus faecalis* (ATCC 29212) and *Staphylococcus aureus* (ATCC 25923)). The antimicrobial activity of AgNPs was analyzed by the minimum inhibitory concentration (MIC). Cultures were grown in exponential phase in nutrient broth at 37°C for 16 h. The various AgNPs concentrations (250  $\mu\text{g}/\text{ml}$ –3.9  $\mu\text{g}/\text{ml}$ ) and *Teucrioside* (250  $\mu\text{g}/\text{ml}$ –3.9  $\mu\text{g}/\text{ml}$ ) were used for antimicrobial tests. The intensity of bacteria was standardized to equal a 0.5 McFarland


standard (approximately  $5 \times 10^7$  organisms  $\text{ml}^{-1}$ ) for each concentration. The bacteria were then inoculated 96 well-plates and were incubated at 37°C for 24 h. After 24 h, the optical density of each well was recorded at 600 nm using a microplate reader [21]. The experiments were repeated three times, and the mean values were used.

## 3. Results and Discussion

### 3.1. Experimental design and optimization of biosynthesis of *Teucrioside*&AgNPs

Design Expert 12 software was used to optimize the synthesis procedure of AgNPs. The experimental design consisted of 46 experiments for five independent variables (pH,  $\text{AgNO}_3$  concentration, *Teucrioside*/ $\text{AgNO}_3$  ratio, microwave power and time). The absorbance data obtained from the UV-spectrum were used as optimization criteria. The acquired data coincided with the quadratic polynomial model and various statistical parameters were used to fit the analysis. After data modeling which is demonstrating the existence of interaction and curvature effect was performed, polynomial equation was generated for response factor. The data obtained overlap the empirical model with correlation coefficient ( $r^2$ ) values of 0.9898. The model diagnostic graphs for response are shown in Figure 1, showing that the data is parallel to the selected model.


$$\begin{aligned} \text{%Yield} = & 46,504 + 2,07969 * A + -7,79367 * B + -0,126277 * C + 11,5005 * D + 34,5181 \\ & * E + -4,87543 * AB + 2,33788 * AC + 6,63818 * AD + 3,17526 * AE \\ & + -2,65788 * BC + -0,543163 * BD + -8,75 * BE + -13,25 * CD + 1,00232 \\ & * CE + 10 * DE + 0,305598 * A^2 + 1,61369 * B^2 + 1,11769 * C^2 + 6,85954 \\ & * D^2 + -14,46 * E^2 \end{aligned}$$

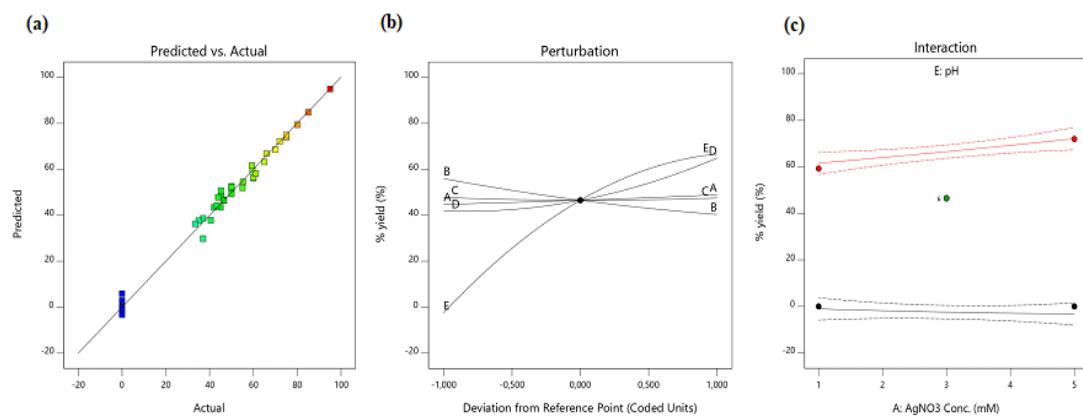

**Figure 1.** The graphs showing (a) predicted vs. actual plot, (b) perturbation chart, (c) interaction plot for response values

Response surface analysis was obtained using 3D response surface plots which elucidated the existence of interactions among the factors and their impacts on the response factor. 3D response surface plots of particle formation (% Yield) of synthesized AgNPs as a function of pH,  $\text{AgNO}_3$  concentration, *Teucrioside*/ $\text{AgNO}_3$  ratio, microwave power and time are shown in Figure 2. It is seen that the effect of pH on the yield of nanoparticle formation is quite high (Figure 2 d, g, i, j). Nanoparticle formation is very low at acidic pH in all parameters. In all experiments where pH is above 7, it is seen that the increase in  $\text{AgNO}_3$


concentration, *Teucrioside*/ $\text{AgNO}_3$  ratio, microwave power and time parameters increases the particle formation efficiency. The dependence of the nanoparticle formation rate on the pH of the solution has also been reported in the literature. According to these studies, nucleation of silver nanoparticles occurs in alkaline conditions, while nanoparticle aggregation is performed in acidic conditions. When examined in terms of nanoparticle efficiency, there was no nanoparticle formation in the acidic range, but it caused a gradual increase in nanoparticle production with the increase in pH [18, 22, 23].

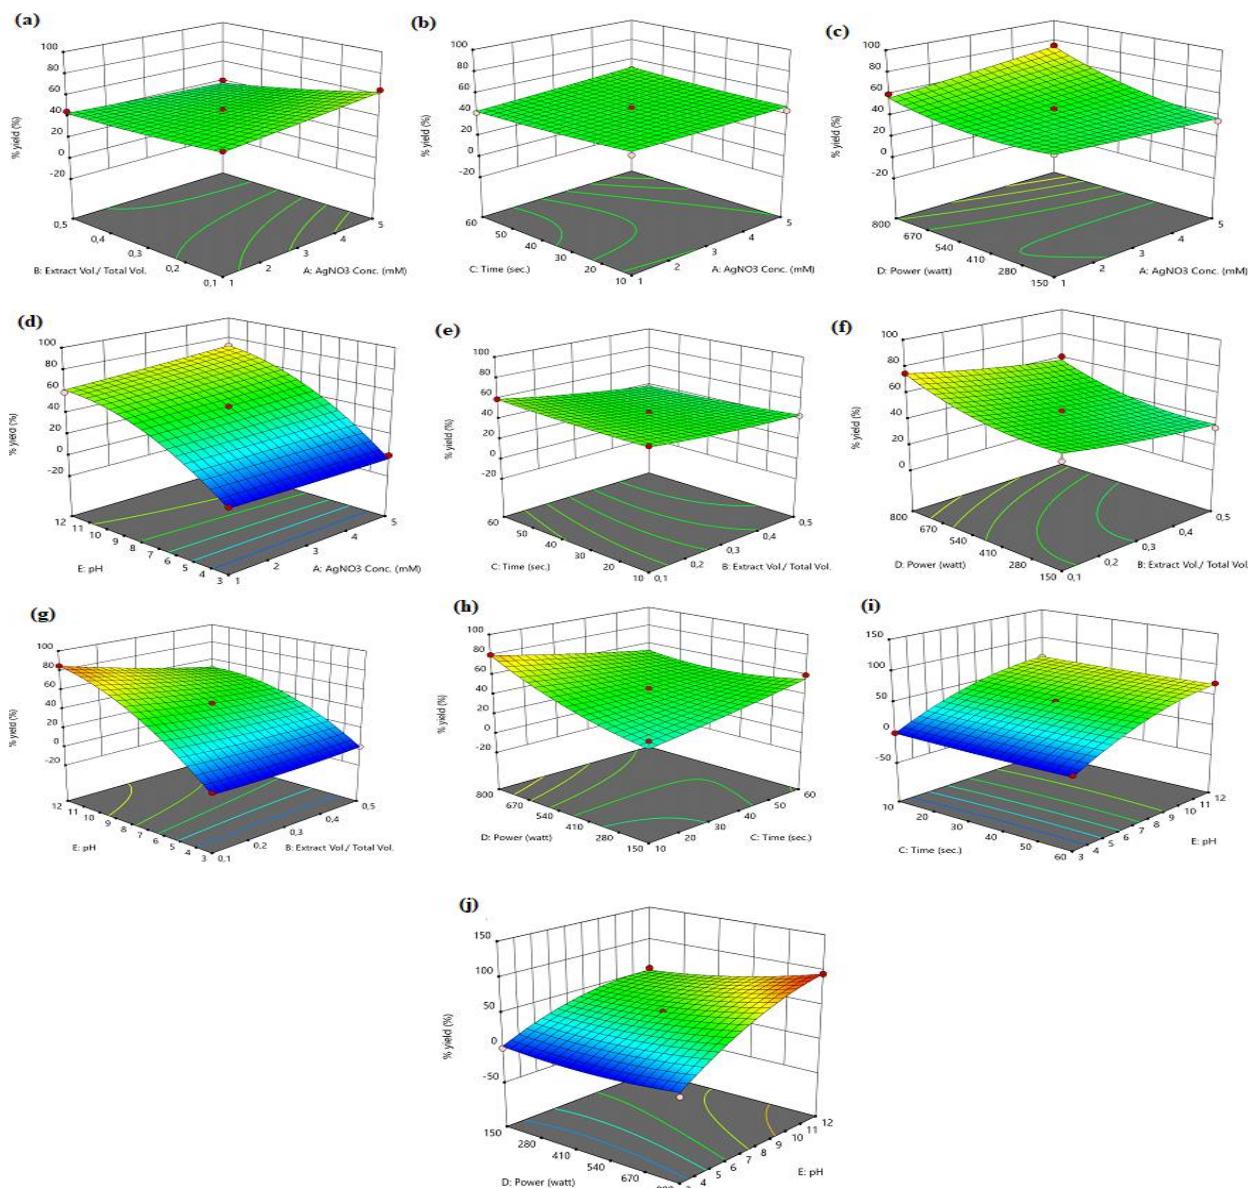

**Figure 2.** 3D response surface plots of particle formation (% Yield) of synthesized silver nanoparticles as a function of pH,  $\text{AgNO}_3$  concentration, *Teucrioside*/ $\text{AgNO}_3$  ratio, microwave power and time. (a)  $\text{AgNO}_3$  concentration and Extract vol./Total vol. (b).  $\text{AgNO}_3$  concentration and time (c).  $\text{AgNO}_3$  concentration and power (d)  $\text{AgNO}_3$  concentration and pH (e) Extract vol./Total vol. and time (f) Extract vol./Total vol. and power (g) Extract vol./Total vol. and pH (h) Time and power (i) pH and time (j) pH and power.

The AgNPs were optimized and then their values were evaluated to identify with numerical optimization. It was seen that the desirability function value was close to 1 and the goal for the response variable was achieved. As the optimized silver nanoparticles


synthesis setting, the overlay plot showed the yellow color area as the optimized area along with the flagged point displaying 5 mM AgNO<sub>3</sub>, *Teucrioside* volume/total volume:0.3, 475 watt, 60 sec. and pH:7.5 were optimal reaction parameters in Figure 3.

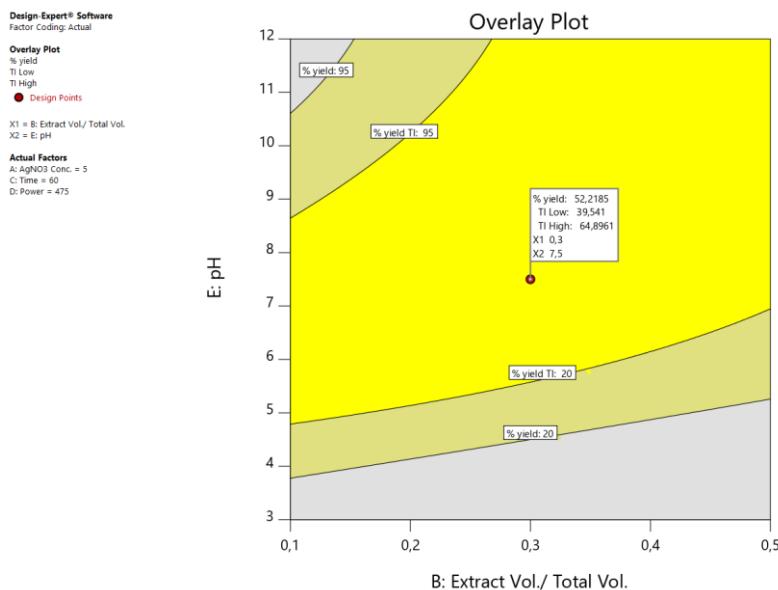

**Figure 3.** The graphs showing yellow color area as the optimized area and flagged point as the selected *Teucrioside*&AgNPs

### 3.2. Characterization of *Teucrioside*&AgNPs


The obtained AgNPs as a result of optimization were characterized by UV-VIS spectrophotometry and the result was shown in Figure 4. The spectrum indicating the peak was observed at 421 nm and this result was fitting with brownish color of the nanoparticles.

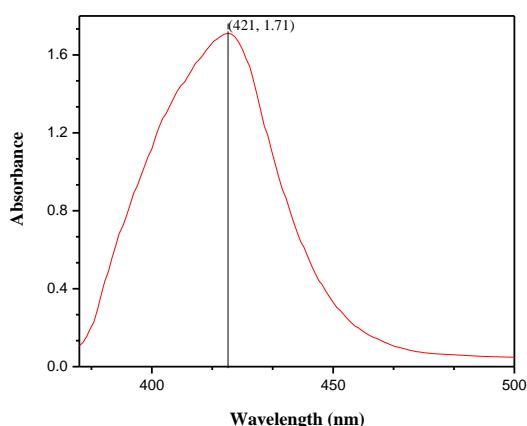


**Figure 4.** UV-Visible spectra of *Teucrioside*&AgNPs

FTIR spectrum of the was shown in Figure 5. The significant absorption bands for silver nanoparticles were observed at 2901.38, 1630.52 and 1399.1. The optimized silver nanoparticles were exhibited a wide absorption band of -OH groups at 3268.75. The absorption bands at 2901.38 and 2986.23 were associated with C-H stretching of aliphatic -CH, -CH<sub>2</sub> groups. The absorption peaks at 1630.52 and 1399.1 were assigned to the asymmetrical and symmetrical -COO stretching of carboxylate compounds in *Teucrioside*.

The size of the prepared silver nanoparticle was determined using dynamic light scattering as shown in Figure 6. The average size of the synthesized AgNPs was  $165.9 \pm 3.1$  nm. The nanoparticles showed homogeneous distribution (polydispersity index:  $0.508 \pm 0.028$ ). Also, the zeta potential value of the synthesized AgNPs was found to be  $-31.5 \pm 0.7$  mV. A negative charge on the surface of the produced nanoparticles indicates that they have high stability.

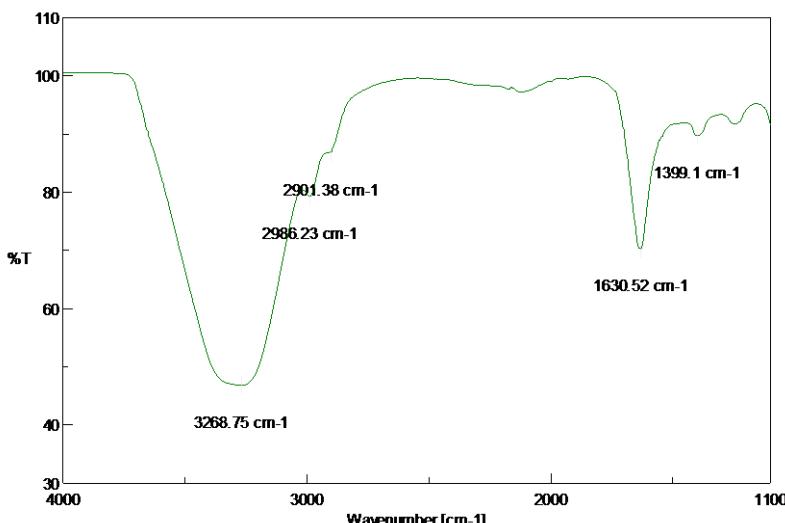

**Figure 5.** FTIR spectra of *Teucrioside&AgNPs*

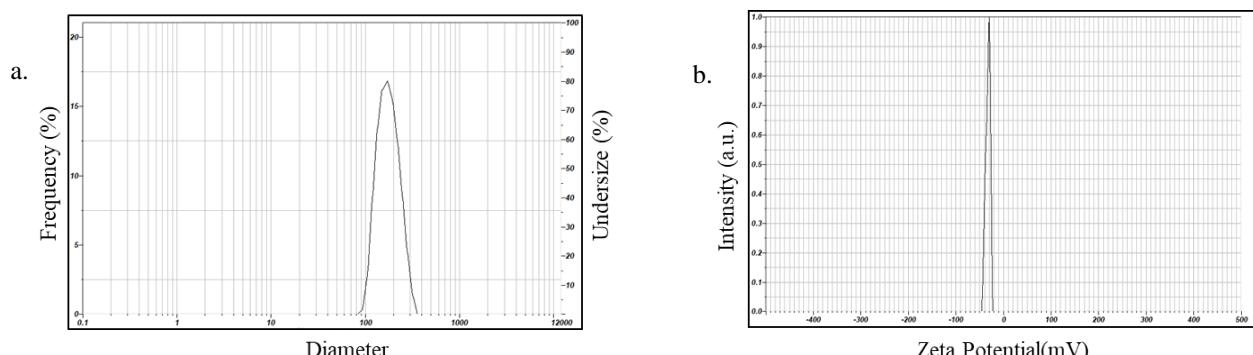


**Figure 6.** Dynamic light scattering (DLS) and zeta potential of *Teucrioside&AgNPs* a. DLS of *Teucrioside&AgNPs* and b. Zeta potential of *Teucrioside&AgNPs*

### 3.3. Antibacterial activity of *Teucrioside&AgNPs*


Growth inhibition curves of pathogenic microorganisms treated with *Teucrioside* extract and *Teucrioside&AgNPs* were shown in Figure 7. Our results show that the produced AgNPs have significant antimicrobial activity against different bacterial

strains. *Teucrioside* concentration of 250  $\mu\text{g}/\text{ml}$  inhibited just % 15 of the *K. pneumoniae* strain, % 2 of *S. aureus* strain and *P. aeruginosa* strain and there was no influence on *E. faecalis* strain (Figure 7a). However, the optimized *Teucrioside&AgNPs* at concentration of 125  $\mu\text{g}/\text{ml}$  completely inhibited all of the bacteria strains (Figure 7b).

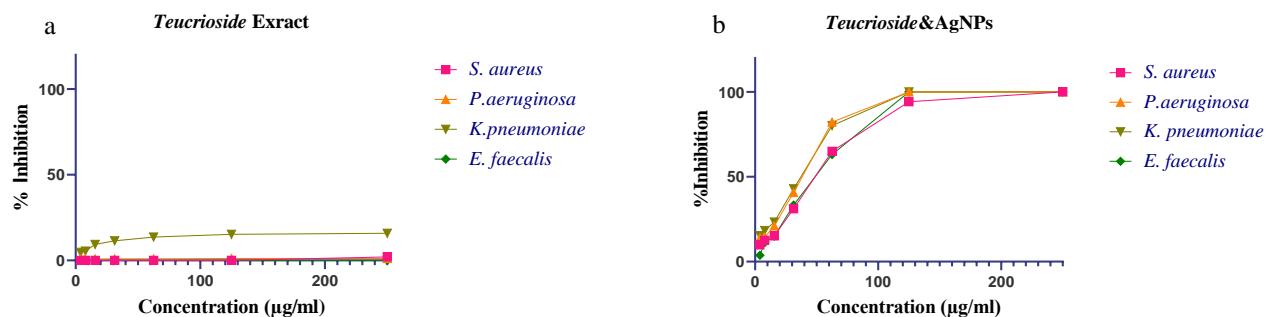

**Figure 7.** Growth inhibition curves of pathogenic microorganisms exposed to *Teucrioside* extract and *Teucrioside&AgNPs* a. Growth inhibition curves of pathogenic microorganisms exposed to *Teucrioside* extract b. Growth inhibition curves of pathogenic microorganisms exposed to *Teucrioside&AgNPs*

Minimum inhibitory concentrations (MIC) of the produced AgNPs were given in Figure 8. When the MIC values are examined, it is seen that *Teucrioside*&AgNPs are effective on gram negative bacteria (*Pseudomonas aeruginosa* and *Klebsiella pneumonia*) than gram positive bacteria (*Enterococcus faecalis* and *Staphylococcus aureus*) at relatively lower concentrations. The more effective antimicrobial activity of silver nanoparticles against gram negative bacteria is likely due to their shape and size [24].

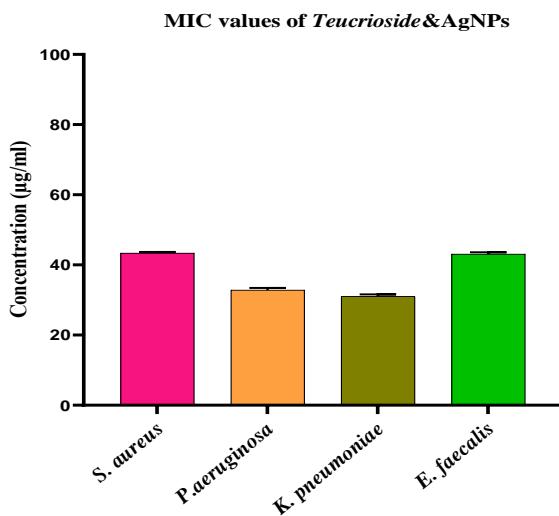

**Figure 8.** MIC value of *Teucrioside*&AgNPs

MIC values of *Teucrioside*&AgNPs were determined as  $42.91 \pm 6.85$   $\mu\text{g}/\text{ml}$ ,  $32.03 \pm 8.36$   $\mu\text{g}/\text{ml}$ ,  $30.14 \pm 8.848$   $\mu\text{g}/\text{ml}$  and  $42.30 \pm 6.75$   $\mu\text{g}/\text{ml}$ , respectively on *S. aureus*, *P. aeruginosa*, *K. pneumonia* and *E. faecalis*. There are numerous studies on the antimicrobial effects of synthesized silver nanoparticles from various biological materials. The obtained MIC values in our study are acceptable when compared to the previously stated concentrations of 10-100  $\mu\text{g}/\text{ml}$  [2, 5, 6, 8, 25]. The results clearly demonstrated that *Teucrioside*&AgNPs have strong antibacterial potential.

#### 4. Conclusions

Silver nanoparticles have attractive physicochemical properties and are often used in biology and medicine because of these properties. Silver nanoparticles play an important role in the development of new antibacterial against pathogenic microorganisms. In this study, *Teucrioside*&AgNPs were synthesized by *Teucrioside* using as a biological reduction agent. The synthesized silver nanoparticles were systematically optimized by Design Expert 12.0 software. The experimental design consisted of 46 experiments for five independent variables (pH,  $\text{AgNO}_3$  concentration, *Teucrioside*/ $\text{AgNO}_3$  ratio, microwave power and time). It was observed that the pH value was highly effective in the yield of nanoparticle formation. Also, an

increase in nanoparticle formation efficiency was observed with increasing  $\text{AgNO}_3$  concentration, *Teucrioside*/ $\text{AgNO}_3$  ratio, microwave power and time. The optimum conditions were determined as 5 mM  $\text{AgNO}_3$ , *Teucrioside* volume/total volume:0.3, 475 watt, 60 sec. and pH:7.5. The mean size and zeta potential of the synthesized AgNPs were  $165.9 \pm 3.1$  nm and  $-31.5 \pm 0.7$  mV, respectively. The antibacterial activity of *Teucrioside*&AgNPs and *Teucrioside* were showed against gram positive and gram negative bacteria strains. Obtained results demonstrated *Teucrioside*&AgNPs exhibit potential as a new antibacterial agent.

#### Acknowledgment

We would like to thank Prof. Dr. Mahfuz Elmastaş and his team for giving us the *Teucrioside*.

#### Conflicts of interest

The authors declare that they have no conflict of interest.

#### References

- [1] Zhang X. F., Liu Z. G., Shen W., Gurunathan S., Silver Nanoparticles: Synthesis, Characterization, Properties, Applications, and Therapeutic Approaches., *Int J. Mol. Sci.*, 17 (2016) 1534-1568.
- [2] Das G., Patra J. K., Shin H. S., Biosynthesis and potential effect of fern mediated biocompatible silver nanoparticles by cytotoxicity, antidiabetic, antioxidant and antibacterial, studies, *Mater. Sci. Eng. C. Mater. Biol. Appl.*, 114 (2020) 111011.
- [3] Panacek A., Smekalova M., Vecerova R., Bogdanova K., Roderova M., Kolar M., Kilianova M., Hradilova S., Froning J. P., Havrdova M., Prucek R., Zboril R., Kvitek L., Silver nanoparticles strongly enhance and restore bactericidal activity of inactive antibiotics against multiresistant Enterobacteriaceae, *Colloids Surf B Biointerfaces*, 142 (2016) 392-399.
- [4] Wang Y., Li Z., Yang D., Qiu X., Xie Y., Zhang X., Microwave-mediated fabrication of silver nanoparticles incorporated lignin-based composites with enhanced antibacterial activity via electrostatic capture effect, *J. Colloid Interface Sci.*, 583 (2020) 80-88.
- [5] Elgamouz A., Idriss H., Nassab C., Bihi A., Bajou K., Hasan K., Abu Haija M., Patole S.P., Green Synthesis, Characterization, Antimicrobial, Anti-Cancer, and Optimization of Colorimetric Sensing of Hydrogen Peroxide of Algae Extract Capped Silver Nanoparticles, *Nanomaterials (Basel)*, 10 (2020).

[6] Dube P., Meyer S., Madiehe A., Meyer M., Antibacterial activity of biogenic silver and gold nanoparticles synthesized from *Salvia africana-lutea* and *Sutherlandia frutescens*, *Nanotechnology*, 31 (2020) 505-607.

[7] Alqahtani M. A., Al Othman M. R., Mohammed A. E., Bio fabrication of silver nanoparticles with antibacterial and cytotoxic abilities using lichens, *Sci. Rep.*, 10 (2020) 16781.

[8] Garibo D., Borbon-Nunez H. A., de Leon J. N. D., Garcia Mendoza E., Estrada I., Toledano-Magana Y., Tiznado H., Ovalle-Marroquin M., Soto-Ramos A. G., Blanco A., Rodriguez J. A., Romo O. A., Chavez-Almazan L. A., Susarrey-Arce, A., Green synthesis of silver nanoparticles using *Lysiloma acapulcensis* exhibit high-antimicrobial activity, *Sci. Rep.*, 10 (2020) 12805.

[9] Willyard C., The drug-resistant bacteria that pose the greatest health threats, *Nature*, 543 (2017) 15.

[10] Xiu Z. M., Zhang Q. B., Puppala H. L., Colvin V. L., Alvarez P. J. Negligible particle-specific antibacterial activity of silver nanoparticles, *Nano Lett.*, 12 (2012) 4271-4275.

[11] Dzul-Erosa M. S., Cauich-Diaz M. M., Razo-Lazcano T. A., Avila-Rodriguez M., Reyes-Aguilera J. A., Gonzalez-Munoz M. P., Aqueous leaf extracts of *Cnidoscolus chayamansa* (Mayan chaya) cultivated in Yucatan Mexico. Part II: Uses for the phytomediated synthesis of silver nanoparticles, *Mater. Sci. Eng. C. Mater. Biol. Appl.*, 91 (2018) 838-852.

[12] Amooaghiae R., Saeri M. R., Azizi M., Synthesis, characterization and biocompatibility of silver nanoparticles synthesized from *Nigella sativa* leaf extract in comparison with chemical silver nanoparticles, *Ecotoxicol Environ. Saf.*, 120 (2015) 400-408.

[13] Elmastas M., Erenler R., Isnac B., Aksit H., Sen O., Genc N., Demirtas I., Isolation and identification of a new neo-clerodane diterpenoid from *Teucrium chamaedrys* L., *Nat. Prod. Res.*, 30 (2016) 299-304.

[14] Antognoni F., Iannello C., Mandrone M., Scognamiglio M., Fiorentino A., Giovannini P. P., Poli F., Elicited *Teucrium chamaedrys* cell cultures produce high amounts of teucrioside, but not the hepatotoxic neo-clerodane diterpenoids, *Phytochemistry*, 81 (2012) 50-59.

[15] Bedir E., Lata, H., Schaneberg B., Khan I. A., Moraes R. M., Micropropagation of *Hydrastis canadensis*: Goldenseal a North American endangered species, *Planta Med.*, 69 (2003) 86-88.

[16] Erden Tayhan S., Bilgin S., Elmastaş M., Evaluation of the Wound Healing Potential of Teucrioside, *Int. J. Chem. Technol.*, 2(1) (2018) 16-19.

[17] Hormozi-Nezhad M. R., Robatjazi H., Jalali-Heravi M., Thorough tuning of the aspect ratio of gold nanorods using response surface methodology, *Anal Chim Acta*, 779 (2013) 14-21.

[18] Nikaeen G., Yousefinejad S., Rahmdel S., Samari F., Mahdavinia S., Central Composite Design for Optimizing the Biosynthesis of Silver Nanoparticles using *Plantago major* Extract and Investigating Antibacterial, Antifungal and Antioxidant Activity, *Sci. Rep.*, 10 (2020) 9642.

[19] Hashemi S. H., Kaykhaii M., Jamali Keikha A., Sajjadi Z., Mirmoghaddam M., Application of response surface methodology for silver nanoparticle stir bar sorptive extraction of heavy metals from drinking water samples: a Box-Behnken design, *Analyst*, 144 (2019) 3525-3532.

[20] Sivagnanam S. P., Getachew A. T., Choi J. H., Green Synthesis of Silver Nanoparticles from Deoiled Brown Algal Extract via Box-Behnken Based Design and Their Antimicrobial and Sensing Properties, *Green Process Synth.*, (2017) 147-160.

[21] Wiegand I., Hilpert K., Hancock R. E., Agar and broth dilution methods to determine the minimal inhibitory concentration (MIC) of antimicrobial substances, *Nat Protoc.*, 3 (2008) 163-175.

[22] Bhutto A. A., Kalay S., Sherazi S. T. H., Culha M., Quantitative structure-activity relationship between antioxidant capacity of phenolic compounds and the plasmonic properties of silver nanoparticles, *Talanta*, 189 (2018) 174-181.

[23] Parthiban E., Manivannan N., Ramanibai R., Mathivanan N., Green synthesis of silver-nanoparticles from *Annona reticulata* leaves aqueous extract and its mosquito larvicidal and anti-microbial activity on human pathogens, *Biotechnol Rep.*, 21 (2019) 297-301.,

[24] Manosalva N., Tortella G., Cristina Diez M., Schalchli H., Seabra A. B., Duran N., Rubilar O., Green synthesis of silver nanoparticles: effect of synthesis reaction parameters on antimicrobial activity, *World J. Microbiol. Biotechnol.*, 35 (2019) 88.

[25] Mousavi S. M., Hashemi S. A., Ghasemi Y., Atapour A., Amani A. M., Savar Dashtaki A., Babapoor A., Arjmand O., Green synthesis of silver nanoparticles toward bio and medical applications: review study, *Artif Cells Nanomed. Biotechnol.*, 46 (2018) 855-872.